

Proton exchange membrane fuel cells with chromium nitride nanocrystals as electrocatalysts

Hexiang Zhong, Xiaobo Chen, Huamin Zhang, Meiri Wang, and Samuel S. Mao

Citation: *Appl. Phys. Lett.* **91**, 163103 (2007); doi: 10.1063/1.2800288

View online: <http://dx.doi.org/10.1063/1.2800288>

View Table of Contents: <http://apl.aip.org/resource/1/APPLAB/v91/i16>

Published by the [American Institute of Physics](#).

Related Articles

Investigation into the gas diffusion electrodes of polymer electrolyte membrane fuel cell under long-term durability test

[J. Renewable Sustainable Energy 2, 013110 \(2010\)](#)

Synthesis and characterization of proton conducting inorganic-organic hybrid nanocomposite films from mixed phosphotungstic acid/phosphomolybdic acid/tetramethoxysilane/3-glycidoxypropyltrimethoxysilane/phosphoric acid for H₂/O₂ fuel cells

[J. Renewable Sustainable Energy 1, 063106 \(2009\)](#)

Performance comparison between planar and tubular-shaped ambient air-breathing polymer electrolyte membrane fuel cells using three-dimensional computational fluid dynamics models

[J. Renewable Sustainable Energy 1, 023105 \(2009\)](#)

Proton exchange membrane fuel cell modeling based on adaptive focusing particle swarm optimization

[J. Renewable Sustainable Energy 1, 013105 \(2009\)](#)

Combinatorial electrochemical cell array for high throughput screening of micro-fuel-cells and metal/air batteries

[Rev. Sci. Instrum. 78, 072209 \(2007\)](#)

Additional information on *Appl. Phys. Lett.*

Journal Homepage: <http://apl.aip.org/>

Journal Information: http://apl.aip.org/about/about_the_journal

Top downloads: http://apl.aip.org/features/most_downloaded

Information for Authors: <http://apl.aip.org/authors>

ADVERTISEMENT



Agilent Technologies

Agilent Education and Research Resources DVD 2012

Packed with over **100 NEW** articles, application notes, webcasts, and videos relating to Renewable Energy, Nanoscience, RF/Wireless, MIMO, Materials, Digital Signals, Photonics, and General Test & Measurement.

Click Here to
Order Your DVD



Agilent Technologies

Proton exchange membrane fuel cells with chromium nitride nanocrystals as electrocatalysts

Hexiang Zhong

Key Materials Laboratory for PEMFCs, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian 116023, China and Graduate School of the Chinese Academy of Sciences, Beijing 100039, China

Xiaobo Chen

Lawrence Berkeley National Laboratory, University of California, Berkeley, California 94720, USA

Huamin Zhang^{a),b)} and Meiri Wang

Key Materials Laboratory for PEMFCs, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian 116023, China

Samuel S. Mao^{a),c)}

Lawrence Berkeley National Laboratory, University of California, Berkeley, California 94720, USA

(Received 26 August 2007; accepted 26 September 2007; published online 15 October 2007)

Polymer electrolyte membrane fuel cells (PEMFCs) are energy conversion devices that produce electricity from a supply of fuel, such as hydrogen. One of the major challenges in achieving efficient energy conversion is the development of cost-effective materials that can act as electrocatalysts for PEMFCs. In this letter, we demonstrate that, instead of conventional noble metals, such as platinum, chromium nitride nanocrystals of fcc structure exhibit attractive catalytic activity for PEMFCs. Device testing indicates good stability of nitride nanocrystals in low temperature fuel cell operational environment. © 2007 American Institute of Physics.

[DOI: 10.1063/1.2800288]

As clean energy conversion devices, polymer electrolyte membrane fuel cells (PEMFCs) have many advantages, including high energy conversion efficiency, which make them attractive for both mobile and stationary applications.^{1,2} Platinum (Pt) has been regarded as the most active catalyst for oxygen reduction reaction, and thus, is widely used to construct the cathode of PEMFCs.^{3–5} However, the ultimate applications of PEMFCs are hindered, at least partially, due to the high cost of the noble material.⁶ Although much progress has been made in reducing Pt usage in the fuel cell anode, lowering the cathode Pt loading generally results in reduced fuel cell efficiency.⁷ Alloying Pt with metals such as Fe, Co, Ni, and Cu has been attempted; however, non-noble metals in these alloys are usually etched easily in the acid environment of PEMFCs. Therefore, the development of unconventional, non-noble catalytic materials that can potentially substitute for Pt is critical for cost-effective fuel cell devices.

Transition metal chalcogenides,^{8,9} metal oxides,¹⁰ and macrocycles such as porphyrin or phthalocyanine¹¹ have been proposed as alternatives to replace noble metals in PEMFCs. Since Levy and Boudart¹² reported Pt-like properties of tungsten carbide, carbides and nitrides have been investigated as potential electrocatalysts.^{13–15} Among different metal nitrides, TiN is the most widely studied,¹⁶ but it suffers from wear and corrosion in acid environment, in addition to its low catalytic activity. In contrast, chromium nitrides such as CrN and Cr₂N have high resistance to wear and corrosion.^{17,18} In this letter, we demonstrate that highly crystalline CrN nanoparticles of fcc structure exhibit attractive

catalytic activity and stability for the oxygen reduction reaction in PEMFCs. This result offers a possible solution to the need of cost-effective electrocatalyst alternatives for fuel cells.

CrN nanocrystals supported on carbon particles (Vulcan XC-72R, Cabot Corp.) were prepared as follows. Carbon particles were impregnated with Cr(NO₃)₃·6H₂O dissolved in water, which were dried at 80 °C for 12 h and calcined for 2 h at 500 °C in N₂ atmosphere. The as-formed powders were treated under NH₃ atmosphere at high temperature for 2 h, and then cooled to room temperature. Figure 1(a) shows x-ray diffraction patterns of CrN on carbon (18 wt % Cr) treated at different temperatures: (a) 800 °C, (b) 900 °C, and (c) 950 °C. All chromium nitride nanocrystals displayed a single fcc CrN phase. Transmission electron microscopy (TEM) studies found that most of the CrN nanocrystals were dispersed over the surface of the carbon particles with diameters ranging from 8 to 30 nm. Figure 1(b) shows two TEM images of CrN on carbon prepared at 800 °C. The formation of relatively large particles could be due to agglomeration of smaller ones when calcinated at high temperature during the preparation process. High-resolution TEM image revealed the highly crystalline nature of CrN nanocrystals, with a typical hexagonal profile, as shown in the inset of Fig. 1(b).

Fuel cell device tests were conducted with 5 cm² membrane electrode assemblies (MEAs) using CrN nanocrystals as the cathode electrocatalyst (Pt was used at the anode). Nafion-1035 (Du Pont) was used as the fuel cell membrane, and the CrN catalysts were mixed with isopropanol and 5% Nafion solution suspension (CrN/C:Nafion=2:1 by dried weight) to form an inklike slurry. The slurry was cast onto a prefabricated gas diffusion layer and heat treated at 130 °C in a vacuum oven to obtain the cathode electrode. The mem-

^{a)} Author to whom correspondence should be addressed.

^{b)} Electronic mail: zhanghm@dicp.ac.cn

^{c)} Electronic mail: ssmao@lbl.gov

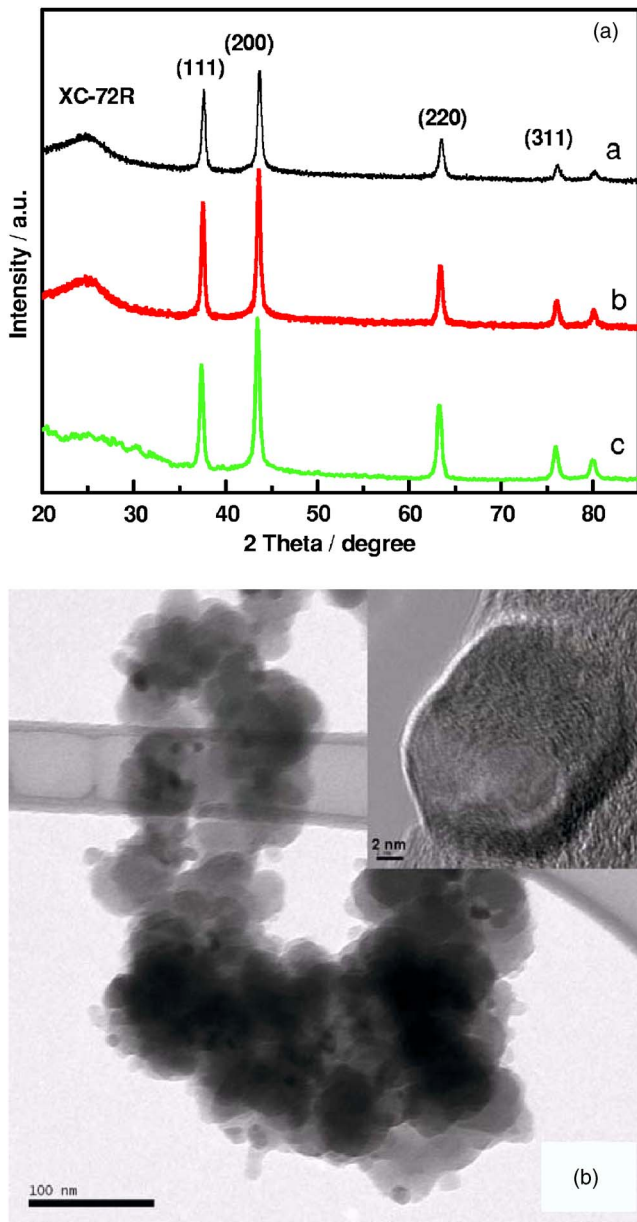


FIG. 1. (Color online) (A) X-ray diffraction patterns of the PEMFC catalyst CrN/C treated at different temperatures: (a) 800 °C, (b) 900 °C, and (c) 950 °C. (B) TEM images of CrN/C prepared at 800 °C. The inset shows a high resolution TEM image of a single CrN nanocrystal.

branes were boiled in 3% H_2O_2 solution and in 0.5M H_2SO_4 to remove organic and mineral impurities, and then rinsed with hot distilled water. The treated membrane was sandwiched between two gas diffusion layers followed by a hot-pressing procedure at 140 °C and 10 MPa to form a MEA. The temperature of the fuel cell devices was kept at 80 °C, and the fuel (H_2) and the oxidant (O_2) were humidified by passing them through water bathes at temperatures of 90 and 85 °C, respectively. Performance data were recorded in the steady state.

Figure 2 shows the performance of fuel cell devices with cathode electrocatalysts prepared under different conditions. Lower temperature processes appear to yield better device performance. With CrN nanocrystals prepared at 800, 900, and 950 °C, the cell voltages are 0.305, 0.289, and 0.275 V, respectively, at a current density of 100 mA cm^{-2} . The corresponding maximum power densities W_{max} are 44.67, 39.4,

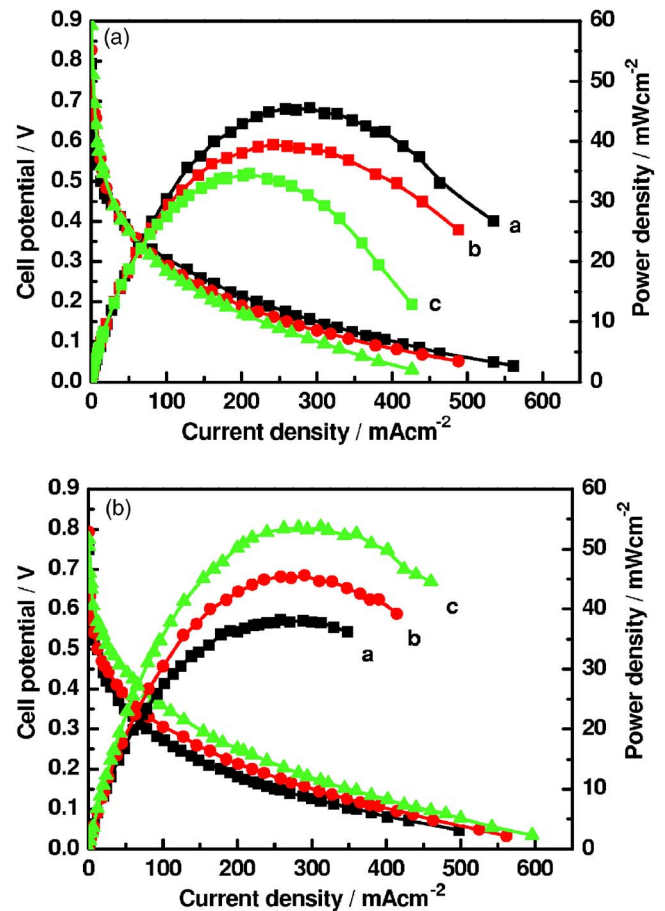


FIG. 2. (Color online) (A) Polarization curves of fuel cell devices with CrN loading of 0.5 mg cm^{-2} prepared at different temperatures: (a) 800 °C, (b) 900 °C, and (c) 950 °C. (B) Polarization curves with different CrN loadings: (a) 0.42 mg cm^{-2} , (b) 0.5 mg cm^{-2} , and (c) 1.08 mg cm^{-2} at 800 °C.

and 34.6 mW cm^{-2} , respectively. The increase of the device performance can be attributed to increased electrochemically active surfaces with smaller nanocrystal size when prepared at lower temperature. On the other hand, better performance was obtained with higher CrN nanocrystal loading of the cathode. The W_{max} increased from 38.84 to 53.66 mW cm^{-2} , and cell voltage increased from 0.240 to 0.318 V at the current density of 100 mA cm^{-2} , when the loading was increased from 0.42 to 1.08 mg cm^{-2} .

The sources of the resistance of the fuel cell devices were studied with the electrochemical impedance spectra (EIS). The EIS in Fig. 3(a) showed that the semicircle was made of two high frequency capacitive loops. The simulated data using equivalent circuits suggested that the resistance at high frequency, as well as the resistance related to electrode structure, remained almost constant when the current increased from 0.5 to 1.5 A. The charge-transfer resistance for oxygen reduction and associated catalyst layer capacitance decreased from 245.6 to 111.2 $\text{m}\Omega$, which indicates that the kinetics of oxygen reduction become faster and contributes to the increase of the cell performance with increased current. However, the value of internal resistance was higher than that of normal Pt-based MEAs.¹⁹ As shown in Fig. 3(b), when saturated with N_2 , the anodic and cathodic electric charges were almost equal, which were responsible for the charge and discharge of an electric double layer. No specific peak due to anodic dissolution was observed in the cyclic voltammetry measurements. This indicated that CrN nano-

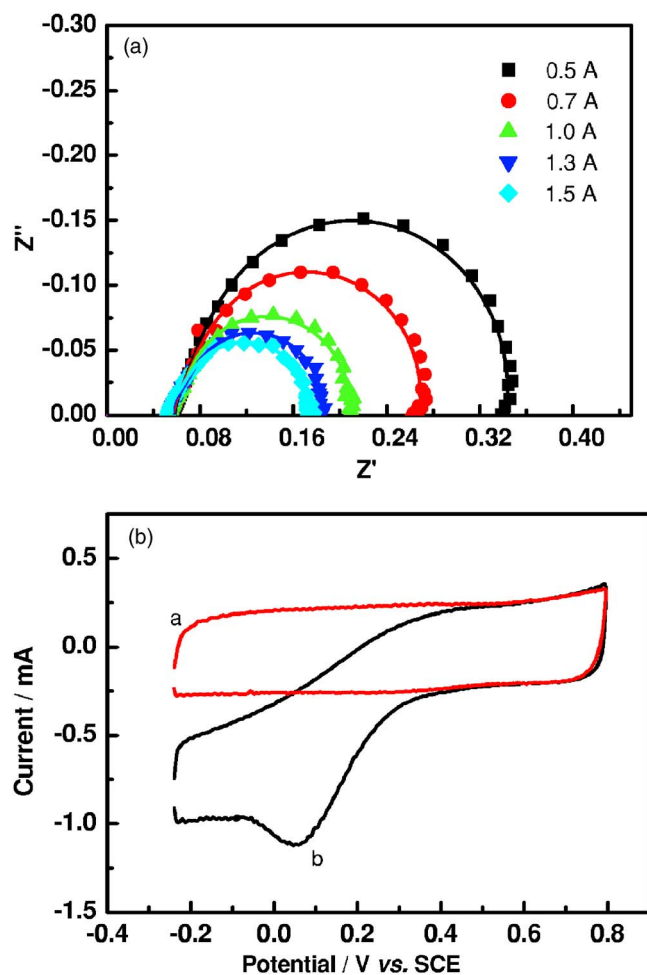


FIG. 3. (Color online) (A) EIS of fuel cell devices with CrN/C prepared at 800 °C at different currents (cell temperature of 80 °C). Legend specifies current of the experiments. (B) Cyclic voltammograms for CrN/C in 0.5 M H₂SO₄ solution at a rotating rate of 900 rpm. (a) Saturated with nitrogen. (b) Saturated with oxygen. Scan rate=5 mV s⁻¹ at 25 °C.

crystals had a high electrochemical stability in acidic solution between the scanned potential ranges. When saturated with O₂, the current increased for the electrode, due to the electroreduction of oxygen. The reaction started at a relatively positive potential, about 0.46 V, which could be attributed to a change in the electron distribution in chromium by addition of nitrogen.^{12,20} This resulted in the creation of base and/or acid sites and yields Pt-like catalytic activity.²¹

To summarize, our measurements have demonstrated that metal nitrides could play an important role in the development of unconventional, non-noble electrocatalysts for cost-effective fuel cell devices. In particular, CrN nanocrystals

displayed attractive Pt-like catalytic activity and stability for PEMFCs. Additional experiments on the reaction kinetics of CrN-based electrode were performed using rotating disk-electrode approach, which indicated a combined kinetic-diffusion mechanism of charge and mass transport. Based on Koutecky-Levich analysis,²² the oxygen was partially reduced to H₂O via the four-electron route at the CrN electrode, and partially reduced to H₂O₂ and then H₂O via the two-electron route. Although the catalytic activity of CrN nanocrystals is somewhat lower than that of Pt, their resource is abundant in addition to their much lower cost. Optimization in nitride preparation processes including composition variations could potentially enhance their catalytic activity, which makes nitride nanocrystals promising for PEMFCs.

We acknowledge support from National Natural Science Foundation of China, Lawrence Berkeley National Laboratory, and the National Center for Electron Microscopy, which is funded by the U.S. Department of Energy under Contract No. DE-AC02-05CH11231.

- ¹S. Litster and N. Djilali, *Electrochim. Acta* **52**, 3849 (2007).
- ²X. G. Yang and C. Y. Wang, *Appl. Phys. Lett.* **86**, 224104 (2005).
- ³G. Chen, D. G. Xia, Z. R. Nie, Z. Y. Wang, L. Wang, L. Zhang, and J. J. Zhang, *Chem. Mater.* **19**, 1840 (2007).
- ⁴K. Kinoshita and J. A. S. Bett, *Carbon* **11**, 403 (1975).
- ⁵Z. Q. Tian, S. P. Jiang, Y. M. Liang, and P. K. Shen, *J. Phys. Chem. B* **110**, 5343 (2006).
- ⁶S. S. Mao and X. B. Chen, *Int. J. Energy Res.* **31**, 619 (2007).
- ⁷H. A. Gasteiger, S. S. Kocha, B. Sompalli, and F. T. Wagner, *Appl. Catal., B* **56**, 9 (2005).
- ⁸D. Cao, A. Wieckowski, J. Inukai, and N. Alonso-Vante, *J. Electrochem. Soc.* **153**, A869 (2006).
- ⁹K. C. Lee, L. Zhang, and J. J. Zhang, *Electrochem. Commun.* **9**, 1704 (2007).
- ¹⁰R. W. Reeve, P. A. Christensen, A. J. Dickinson, A. Hamnett, and K. Scott, *Electrochim. Acta* **45**, 4237 (2000).
- ¹¹R. Bashyam and P. Zelenay, *Nature (London)* **443**, 63 (2006).
- ¹²R. B. Levy and M. Boudart, *Science* **181**, 547 (1973).
- ¹³R. Venkataraman, H. R. Kunz, and J. M. Fenton, *J. Electrochem. Soc.* **150**, A278 (2003).
- ¹⁴S. Arico, S. Srinivasan, and V. Antonucci, *Fuel Cells* **1**, 133 (2001).
- ¹⁵Y. Hara, N. Minami, and H. Itagaki, *Appl. Catal., A* **323**, 86 (2007).
- ¹⁶F. Mazza and S. Trassatti, *J. Electrochem. Soc.* **110**, 847 (1963).
- ¹⁷J. M. Lackner, W. Waldhauser, B. Majorb, J. Morgielb, L. Majorb, H. Takahashic, and T. Shibayama, *Surf. Coat. Technol.* **200**, 3644 (2006).
- ¹⁸K. Volz, M. Kiuchi, and W. Ensinger, *Surf. Coat. Technol.* **108**, 303 (1998).
- ¹⁹O. Antoine, Y. Bultel, and R. Durand, *J. Electroanal. Chem.* **499**, 85 (2001).
- ²⁰G. Soto, W. de la Cruz, F. F. Castillon, J. A. Diaz, R. Machorro, and M. H. Farias, *Appl. Surf. Sci.* **214**, 58 (2003).
- ²¹L. H. Bennett, J. R. Cuthill, A. J. Mcalister, N. E. Erickson, and R. E. Watson, *Science* **184**, 563 (1974).
- ²²M. S. El-Deab and T. Ohsaka, *Electrochim. Acta* **47**, 4255 (2002).